

Carbon-nanotube coatings promise better thermal detectors

JOHN LEHMAN AND ANNE DILLON

With high thermal conductivity and resistance to damage, carbon-nanotube coatings are a promising new technology for thermal detectors. This viable alternative may eventually provide better radiometric standards for laser measurement.

With few exceptions, all of the primary measurement standards for establishing traceability to fundamental units for radiometry are based on thermal detectors (see table). These devices use some form of thermal-absorber coating such as carbon-based paint or a diffuse metal such as gold black.^{1,2} Carbon-nanotube coatings present an alternative to current technologies. Their high thermal conductivity, damage resistance, and reported optical-absorption efficiency make them promising candidates as coatings for thermal detectors.^{3,4} Scientists in the Sources, Detectors and Displays Group of the National Institute of Standards and Technology (NIST; Boulder, CO) have recently demonstrated thermal detectors with absorber coatings consisting of either purified single-wall carbon nanotubes (SWNTs) or multi-wall carbon nanotubes (MWNTs).^{5,6} These SWNTs and MWNTs may form the basis of the next generation of absorber coatings for thermal detectors for high-accuracy optical and thermal radiometry, particularly for high-energy and ultraviolet (UV) laser radiometry. The recent work of the scientists brings together laser-metrology and carbon-nanotube (CNT) research with the goal of developing better

JOHN LEHMAN is project leader for continuous-wave laser radiometry in the Sources, Detectors and Displays Group at the National Institute of Standards and Technology, 325 Broadway, Boulder, CO 80305-3328. ANNE DILLON is senior scientist with the Hydrogen Storage Project at the National Renewable Energy Laboratory, 1617 Cole Blvd., Golden, CO 80401-3393; e-mail: lehman@boulder.nist.gov and anne_dillon@nrel.gov.

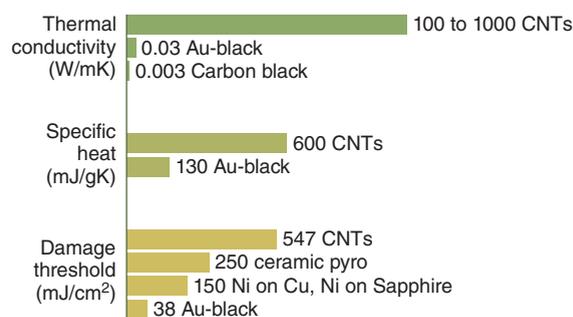


FIGURE 1. The properties of various black coating types provide a guide to understanding the strengths of new carbon-nanotube coating options.

measurement standards and improved techniques for producing CNT coatings using detector-friendly processes.

Traditional black coatings

During the last 50 to 100 years, thermal coatings have been developed from carbon-based paints, diffuse metals (gold black, silver black), and oxidized metals (anodized aluminum) and other materials. In principle, the response as a function of wavelength (the spectral responsivity) of thermal detectors depends on the variation of reflectance of the detector coating as a function of wavelength. The ideal coatings are capable of very low reflectance ranging from 0.2 μm (UV wavelengths) to beyond 50 μm (infrared wavelengths). Such coatings, however, are vulnerable to damage at high optical powers, from forced air (they can be literally blown away), and from aging and hardening at UV wavelengths. When the important properties of thermal detectors are compared (see Fig. 1), the damage threshold and thermal conductivity of MWNTs is many times greater than gold-black- or carbon-based paints.

Carbon-nanotube coating types and processes

Bulk production of carbon single- and multiwall nanotubes has been achieved by a variety of methods, including laser vaporization, arc-discharge evaporation, and various chemical-vapor-deposition (CVD) techniques. Carbon nanotubes can also be deposited directly on metal-catalyst-coated substrates via CVD. In proof-of-concept investigations, puri-



GASIR[®] molded lenses

...the ideal solution for medium to large volume infrared optical systems.

Umicore has developed a unique, single-step molding process to manufacture GASIR[®], a chalcogenide glass, in finished spherical, aspherical and diffractive lens geometry eliminating the need for single-point diamond turning processing.

GASIR[®] offers the infrared market a high-quality, low-cost material solution for optics integrated into high-volume thermal imaging and sensing applications.

Umicore Optics - Belgium

Tel: + 32 14 24 55 97
Fax: + 32 14 24 55 34

Umicore Optical Materials - USA

Tel: (918) 673 1659
Fax: (918) 673 2121

optics@umicore.com
www.optics.umicore.com

THIN-FILM COATINGS, *continued*

fied, bulk SWNTs were applied to a thermal detector with a simple airbrush technique. The promising results of these preliminary investigations motivated the development of CVD techniques for the synthesis of nanotube films directly on thermal-detector surfaces.

Single-wall carbon nanotubes grown by laser vaporization were deposited on a lithium tantalate (LiTaO₃) disc 12 mm in diameter and 60- μ m thick, with nickel (Ni) electrodes 10 mm in diameter and 25-nm thick on each face. A scanning-electron microscope was used to view the sample SWNT bundles that make up the surface of the detector (see Fig. 2). The synthesis of the SWNTs was accomplished using a laser vaporization method (see Fig. 3). The laser vaporization process is similar to that described by Guo et al., in which an alexandrite laser emitting at 755 nm with a power density of 40 W/cm² was used to vaporize a graphite target doped with cobalt (Co; 0.6% relative atomic mass) and Ni (0.6% relative atomic mass).⁷ The crude soot was produced at 1200°C with 500-torr argon (Ar) flowing at 100 cm³/min (units based on standard air). The SWNTs were purified with a nitric acid (HNO₃) reflux for 16 hours, followed by air oxidation at 550°C for 30 minutes.⁸ The purified SWNTs were dispersed in chloroform using a cup-horn sonicator connected to an ultrasonic processor. During the entire sonication period (two hours), the suspensions were kept in a water bath cooled to 15°C. The SWNT (0.1% by weight) suspension was then applied from 3 \times 2 aliquots using an airbrush and dried under a steady stream of nitrogen.

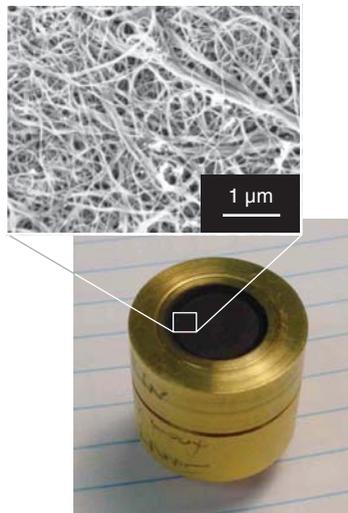


FIGURE 2. One method of coating a pyroelectric detector surface is with single-wall carbon nanotubes (SWNTs) produced by laser vaporization, dispersed in chloroform, and applied with an airbrush.

With the availability of purified nanotubes in bulk form, the prospect of using an airbrush to apply the SWNT coating is very attractive compared to depositing gold black. Unlike the gold-black deposition process, the coating can be applied after the detector is completely assembled, with minimal risk of damage to the detector. After drying, the SWNT coating is not easily dislodged by forced air. Therefore, unlike gold-black-coated detectors, dust can be removed from the detector surface

without damaging the coating.

Hot-wire chemical-vapor deposition (HWCVD), which uses a tungsten filament for the decomposition of various precursor gases, has recently been used for continuous gas-phase production of both SWNTs and MWNTs.^{9, 10} However, by coating various substrates with a transition-metal catalyst (instead of supplying this catalyst in the gas phase), carbon nanotubes can be directly grown onto surfaces using the HWCVD tech-


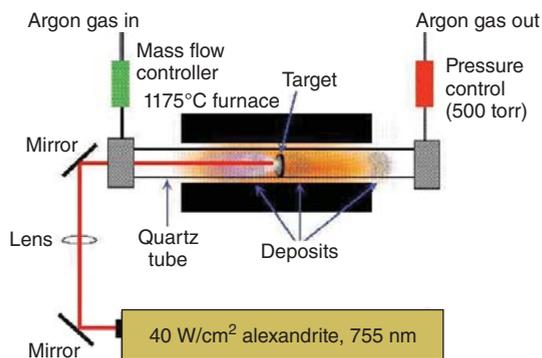


FIGURE 3. The growth of single-wall carbon nanotubes (SWNTs) can be accomplished by a laser vaporization process.

nique (see Fig. 4). Nanotubes directly deposited onto thermal detectors should be more densely packed and provide a more uniform surface than that achieved with the airbrush technique. These proper-

Standards traceability of the NIST laser power and energy calibration ensemble

Laser power and energy range	Primary standard or transfer standard	Industrial application of secondary standards—calibrated from primary standard
1.06 to 10.6 μm 100 W to 200 kW 10 kJ to 6 MJ	BB-Series calorimeter	Military applications, high-power industrial lasers
0.4 to 2 μm 100 μW to 1 mW	Cryogenic radiometer	Optical communications Range finders, target designators, industrial processes, medical lasers
0.4 to 2 μm 50 μW to 1 W 10 mJ to 30 J	C-Series calorimeter	Optical communications Range finders, target designators, industrial processes, medical lasers
0.4 to 2 μm 1 W to 1 kW 300 mJ to 3 kJ	K-Series calorimeter	Industrial processes, medical lasers
1.06 μm 0.5 to 15 J	Q-Series calorimeter	Range finders, target designators, industrial processes, medical lasers
248 nm 0.5 to 15 J	QUV- Series calorimeter	Semiconductor lithography, medical lasers
193 nm 0.5 to 15 J	QDUV-Series calorimeter	Semiconductor lithography, medical lasers
157 nm 0.1 to 15 J	QVUV-Series calorimeter	Semiconductor lithography, medical lasers
0.4 to 2 μm 50 μW to 1 mW	Electrically calibrated pyroelectric detector	Optical communications Industrial processes, medical lasers, night-vision systems
0.2 to 10 μm 50 μW to 1 W 10 mJ to 30 J	Other pyroelectric detectors and thermopiles	Optical communications Industrial processes, medical lasers, night-vision systems.

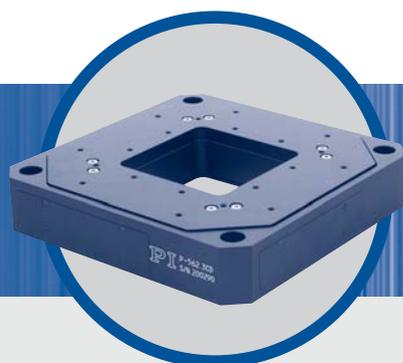

Piezo • Nano • Positioning

PI

PIMars™ High-Speed Piezo-Nanopositioning Stages


Nano-Precision in Milliseconds!

■ Sub-nm Precise ■ Sub-ms Response ■ Parallel Metrology ■ 2D to 6D

www.pi.ws/lfh

Moving the NanoWorld | www.pi.ws

PI (Physik Instrumente) L.P. Tel: (508) 832-3456

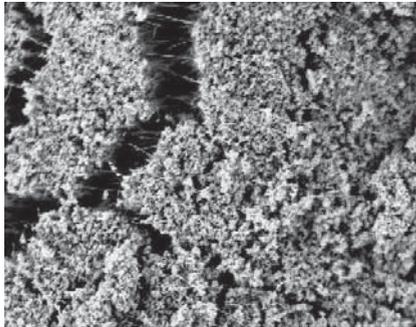

HW55 6 μm 5000X

FIGURE 4. A cross-sectional view of well-aligned carbon nanotubes shows their organized structure.

ties should reduce the reflectivity of the nanotube coatings and allow improved performance.

To demonstrate the process, HWCVD was performed in a quartz-tube reactor enclosed in a clamshell furnace. A single 0.5-mm diameter tungsten filament 23 cm in length was operated at approximately 20 A, 25 V, and at 1700°C as determined by an optical pyrometer.

Nickel (Ni) films were used as a substrate catalyst, ranging in thickness from 50 to 100 Å. Graphitic MWNTs with a modest amount of non-nanotube carbon impurities were produced in an atmosphere of 1:5 methane:argon at 150 torr with the furnace at 400°C.

Performance of carbon-nanotube coatings

The development of our coating is just a part of the enormous challenge of understanding the optical, thermal, and electrical properties of CNTs. Our approach is to investigate the coating behavior based on the detector responsivity and to understand the CNT optical properties based on a specular absorbance rather than the more conventional approach of measuring diffuse reflectance. We are investigating CNT coatings on a variety of thermal-detector platforms including pyroelectric materials, thermopiles, and cavity-like structures for various radiometers and calorimeters.

For these platforms, there are advan-

tages and disadvantages to the nature and method of the coating deposition. Single-wall carbon nanotubes applied by air-brush are desirable because the process is convenient and our detector-fabrication yield is high—the coating can be applied as a final step with little more difficulty than applying spray paint. This is compatible with planar detector platforms, as well as more-complicated optical-trap-like geometries such as a sphere or cone. CVD- and HWCVD-based coatings deposited directly on the detector platform are less desirable from the standpoint of detector fabrication, but possibly more desirable for reasons related to the fundamental detector operation. During the CVD process, the coating deposition is an intermediate step in the overall detector fabrication. The platform must be heated, which presents a risk from the standpoint of thermal stress and other possible damage such as depoling in the case of the pyroelectric crystals, or debonding a thermopile or thermistor junction. We are motivated to overcome these challeng-



Thin Film Center

We also offer customized, on-site Masterclasses year round. These specialty courses are always tailored to meet your individual, or your company's specific needs. Please call us for additional details and pricing information.

Optical Coating Design Classes

September 12 - 16, 2005

Optical Coatings From Design Through Manufacture

September 19 - 21, 2005

Advanced Computer-Aided Design of Optical Coatings

Tucson, Arizona, USA

www.thinfilmcenter.com

Email us at: info@thinfilmcenter.com

 1 520 322 6171
  2745 E Via Rotonda
FAX 1 520 325 8721 Tucson AZ 85716

micro objective focusing with nm-accuracy



motion up to 500μm; max. microobjective diameter 40mm for standard and inverse application

series MIPOS -

THE FASTEST FOCUSING DRIVE



USA
 phone: 508-634-6688
 fax: 508-634-6868
 e-mail: info@piezोजना.com

Germany
 phone: +49 3641-6688-0
 fax: +49 3641-6688-66
 e-mail: info@piezोजना.com

www.piezोजना.com

es because experimental evidence suggests that coatings grown directly on the detector platform will have the highest thermal-coupling efficiency and better damage resistance.

At NIST, we plan to optimize either the HWCVD or CVD process to grow nanotubes directly on a pyroelectric detector and to demonstrate that such a detector is spectrally, spatially, and directionally uniform from the visible wavelength range to beyond 10 μm . Having established this, we can do a greater range-of-detector evaluations including damage testing, thermal conductivity, and thermal diffusivity, and extend this knowledge to other detector platforms. Beyond these practical matters, we also hope to make fundamental contributions to the bigger scientific challenges of determining tube species and purity by measuring optical properties of CNTs.

Collaboration with NREL

Our coinvestigators at the National Renewable Energy Laboratory (NREL; Golden, CO) are regarded as world experts in the growth and characterization of carbon nanotubes because of their ongoing research efforts to develop a nanotube-based vehicular hydrogen storage system. Researcher Anne Dillon at NREL is coauthor of an article, "Hot-wire Chemical Vapor Synthesis for a Variety of Nano-materials with Novel Applications," published in *Thin Solid Films* in October 2004 that includes a discussion of nanotube coatings for thermal detectors. Researchers at NREL fabricated the nanotube coatings discussed here. Future work at NREL will include CVD synthesis of aligned arrays of MWNTs with potential solid-state lighting applications as well as aligned arrays of SWNTs for the fabrication of nanotube-based membranes. Aligned arrays of both types of nanotubes are also promising candidates for the optimization of nanotube thermal detector coatings.

Continuing research at NIST

The current work on CNT coatings will benefit U.S. military standards labs as well as other national measurement institutes around the world that rely on thermal detectors built at NIST. Currently, collaborators at the Navy Surface Warfare Center (Corona, CA) and at the National Physical Laboratory (NPL; Middlesex, England) have expressed interest in this work. The long-term goal of the research at NIST is to create the basis of the next generation of laser calorimeters, radiometers, thermopiles, and pyroelectric detectors (primary and secondary standards), and to anticipate and serve the needs of industry related to laser power and energy measurements.

Carbon nanotubes have been presented in the literature as being the basis for future optical sources, detectors, and displays. NIST believes that it is incumbent on our project to develop the expertise to productively participate in the understanding and development of the CNT field. □

REFERENCES

1. W. R. Blevin and W. J. Brown, *Metrologia* 2, 139 (1966).
2. J. H. Lehman et al., *Meas. Sci. Technol.* 14, 916 (2003).
3. S. Berber et al., *Phys. Rev. Lett.* 84, 4613 (2000).
4. J. S. Kim et al., *Appl. Phys. Lett.* 82, 1607 (2003).
5. J. H. Lehman et al., *Applied Optics* 44, 483 (2004).
6. J. H. Lehman et al., *Infrared Physics and Technology* (November 2004).
7. T. Guo et al., *Chemical Physics Lett.* 243, 49 (1995).
8. A. C. Dillon et al., *Adv. Materials* 11, 1354 (1999).
9. A.H. Mahan et al., *Appl. Phys. Lett.* 81, 4061 (2002).
10. A. C. Dillon et al., *NanoLetters* 3, 1425 (2003).


27 - 28 - 29 SEPTEMBER 2005
Paris-Expo · Porte de Versailles · France

OPTO



THE ONLY EUROPEAN
EXHIBITION DEDICATED
TO ALL OPTICAL SOLUTIONS

R&D · Integration · Convergence · Application

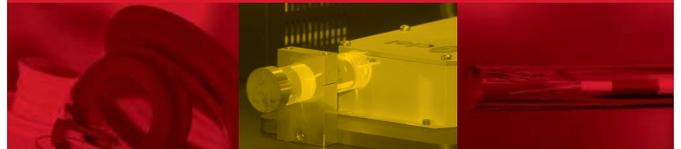

150 Exhibitors - 6 000 Visitors

BIO OPTO, a specific area and conferences dedicated to biophotonics

Bio Opto
Photonique pour le vivant

Bio Opto 2005 will be the meeting place for:

- suppliers of cell and tissue imaging solutions, materials, lasers, optical and optoelectronic components, testing and measuring solutions, instruments and services...

- decision-makers from key user sectors, e.g. food industry, biology, medicine, environment...

Free access badge on:

www.optoexpo.com

Password: PUB

OPTO
1, RUE DU PARC - 92593 LEVALLOIS-PERRET CEDEX
TÉL. : +33 (0)1 49 68 51 00
Fax : +33 (0)1 49 68 54 66



Opto 2005, a trade show
organized by Exposition
www.exposition.fr